arXiv:1301.6062v1 [cond-mat.str-el] 25 Jan 2013

Quantum criticality in a partially geometrically frustrated heavy-fermion system: $\mathbf{CePd_{1-x}Ni_xAl}$

V. Fritsch[1], N. Bagrets[1], G. Goll[1], W. Kittler[1], M. J. Wolf[1], K. Grube[2], C.-L. Huang[1,2] and H. v. Löhneysen[1,2]
[1]*Karlsruher Institut für Technologie, Physikalisches Institut, 76128 Karlsruhe, Germany*
[2]*Karlsruher Institut für Technologie, Institut für Festkörperphysik, 76128 Karlsruhe, Germany*

In the antiferromagnetic (AF) heavy-fermion system system CePdAl the magnetic Ce ions form a network of equilateral triangles in the (001) plane, similar to the kagomé lattice, with one third of the Ce moments not participating in the long-range order. The Néel temperature $T_N = 2.7\,K$ is reduced upon replacing Pd by Ni in $CePd_{1-x}Ni_xAl$, with $T_N \to 0$ for $x = 0.144$. At this concentration the specific heat C exhibits a $C/T \propto -\log T$ dependence. Within the Hertz-Millis-Moriya model of quantum criticality, this behavior might indicate 2D critical antiferromagnetic fluctuations, which might arise from the decoupling of the 3D magnetic order by frustration. On the other hand the simultaneous presence of Kondo effect and magnetic geometric frustration might entail a new route to quantum criticality.

Quantum phase transitions (QPT) have received a lot of attention in recent years [1–3]. An issue of current interest is the role of dimensionality when a system is approaching a quantum critical point (QCP). A particularly compelling case is given by heavy-fermion (HF) systems where the transition between a magnetically ordered ground state and a paramagnetic Fermi-liquid state is driven by the competition between intersite Ruderman-Kittel-Kasuya-Yosida (RKKY) and on-site Kondo interactions, which can be tuned by external pressure or chemical composition [3]. Unconventional quantum critical behavior was observed in the canonical HF system $CeCu_{6-x}Au_x$ where quasi-2D magnetic fluctuations arise out of 3D long-range antiferromagnetic (AF) order, as shown by inelastic neutron scattering [4]. Furthermore, the QCP is associated with unusual energy/temperature scaling of the dynamical susceptibility arising from critical fluctuations [5, 6]. These findings prompted the development of alternative models of quantum criticality [7, 8] going beyond the Landau-Ginzburg-Wilson model of classical second-order phase transitions and its extension to QPTs at zero temperature by Hertz [9], Millis [10] and Moriya [11] (HMM model). In the model of local quantum criticality derived within the framework of extended dynamical mean-field theory [8], 2D fluctuations are a prerequisite for the validity of the model. The issue of dimensional crossover in metallic quantum-critical magnets was discussed theoretically by Garst *et al.* [12]. The issue of dimensionality was also addressed recently by comparing several systems of reduced dimensionality with cubic $Ce_3Pd_{20}Si_6$ at a magnetic QCP [13].

Geometric frustration is a possible means to access quantum critical behavior in magnets on more general terms, with the possible appearance of spin liquids, e.g., in kagomé lattices [14]. Consequently, a more general ('global') phase diagram of quantum criticality was predicted [15–17]. Hence it is of considerable interest to study quantum criticality in HF systems with partial frustration. First experiments were done recently on Ce_2Pt_2Pb, a realization of the Shastry-Sutherland model, without however accessing quantum critical behavior [18].

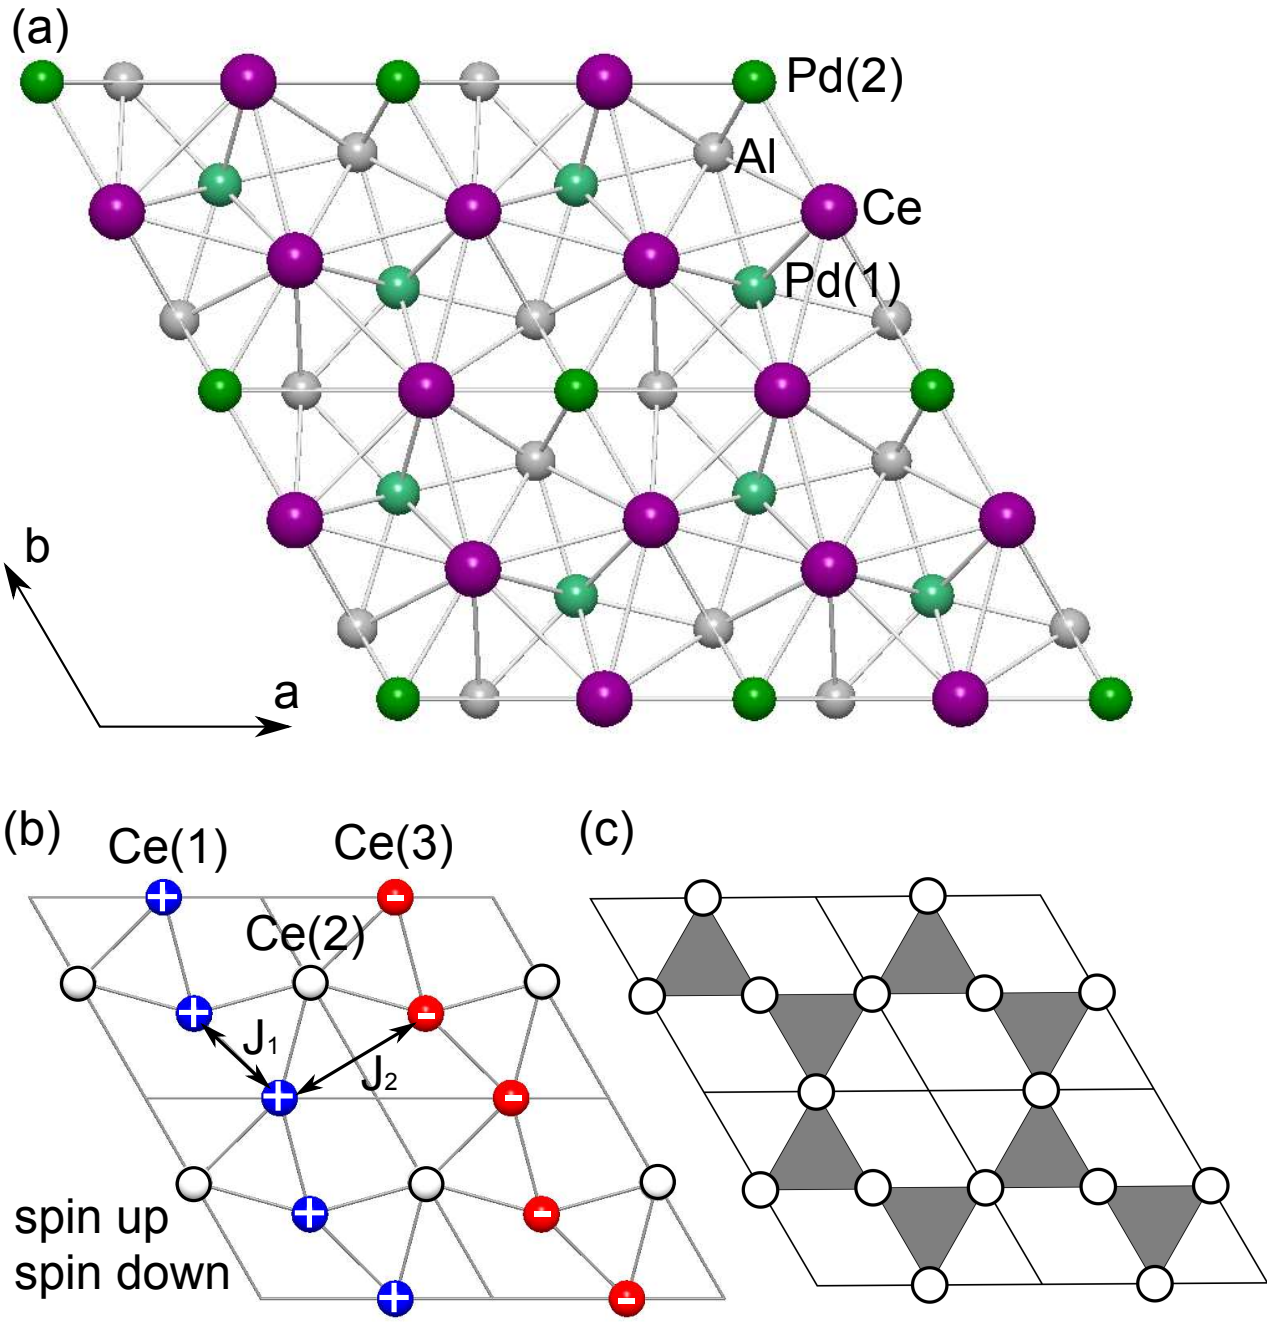

FIG. 1. (a) View on the *ab* plane of CePdAl. The Ce and Pd(2) atoms form a plane at $z = 0$, the Al and Pd(1) atoms form a plane at $z = 1/2$. (b) View on the *ab*-plane, showing one of the three symmetry-related magnetic structures. Only Ce-atoms are shown for clarity. (c) Kagomé lattice for comparison.

In this paper we investigate the quantum critical behavior of partially frustrated CePdAl, a HF system with a distorted kagomé lattice, see Fig. 1 (a). In the hexagonal ZrNiAl-type crystal structure of CePdAl, the magnetic Ce ions form a network of equilateral corner-sharing triangles in the *ab* plane [19, 20], see Fig. 1 (b). The compound exhibits a strong magnetic anisotropy with the susceptibility ratio $\chi_c/\chi_{ab} \approx 14$ which is attributed to crystalline-electric-field and exchange anisotropies [21]. CePdAl exhibits Kondo-lattice properties as evidenced by an increase of the electrical resistivity towards low temperature yielding a Kondo-temperature $T_{\mathrm{K}} \approx 5$ K [22], and orders antiferromagnetically below $T_{\mathrm{N}} = 2.7\,\mathrm{K}$. A partially ordered magnetic state of CePdAl was first revealed by neutron diffraction measurements on powder samples [20], where one third of the Ce moments do not participate in the long-range order. The magnetic structure of CePdAl consists of three inequivalent Ce sites, with a magnetic ordering vector $\mathbf{Q} = (\frac{1}{2}\ 0\ \tau)$ with $\tau \approx 0.35$ being weakly temperature dependent [23]. Within a single kagomé-like layer, one thus has ferromagnetic chains coupled antiferromagnetically (see Fig. 1 (b)). A recent thorough ^{27}Al NMR study indicated that the partially ordered state is indeed stable down to at least 30 mK (Ref. 24).

The nearest-neighbor (nn) and next-nearest neighbor (nnn) Ce-Ce distances within the basal plane are reported as $d_{ab1} = 3.73\,\mathrm{Å}$ and $d_{ab2} = 5.25\,\mathrm{Å}$ respectively [20, 25]. The interplane nn distance is $d_{\perp} = 4.24\,\mathrm{Å}$ [20]. Neglecting the interplane interactions the magnetic structure can be described in terms of a purely 2D model with nn ferromagnetic (J_1) and nnn AF (J_2) interactions within the ab plane [26], see Fig. 1 (b). The competition between Kondo and RKKY interactions was modeled in this approach by a T-dependent on-site parameter $\Delta_i(T)$. The effect of geometric frustration on this competition was recently studied in detail by variational Monte Carlo simulations [27]. Unfortunately, a model incorporating the interplane coupling $J_{\perp}$ to be compared with the experimentally determined magnetic structure does not exist up to now. The QCP of CePdAl can be accessed by partial substitution of Pd by Ni [28, 29]. We find that T_{N} of CePdAl is monotonically reduced to $T = 0$ with increasing Ni content. At the critical concentration $x_c \approx 0.144$, the specific heat C as a function of temperature T varies as $C/T \propto \log(T_0/T)$, within the HMM model suggestive of 2D critical fluctuations.

Polycrystalline samples of CePd$_{1-x}$Ni$_x$Al were prepared by arc-melting appropriate amounts of the pure elements Ce(99.9) [30], Pd(99.95), Ni(99.95), Al(99.999) under argon atmosphere with titanium gettering. To achieve homogeneity, the samples were turned over after melting and solidifying and remelted several times. The total weight loss after preparation did not exceed 0.5%. The CePd$_{1-x}$Ni$_x$Al samples were investigated in the as-cast state since annealing may cause a change of their structure [31]. All samples were characterized by powder x-ray diffraction and atom absorption spectroscopy (AAS). They revealed the single-phase ZrNiAl structure ($P\overline{6}2m$) of the parent compounds CePdAl and CeNiAl. AAS was used to determine the actual Ni concentrations x, that are quoted throughout this paper. The lattice constants a and c and the unit-cell volume V approximately follow Vegard's law in the concentration range investigated ($x < 0.15$). Specific-heat measurements were performed in a dilution refrigerator in the temperature range $0.05 \leq T \lesssim 2.5$ K using the standard heat-pulse technique. A Physical Properties Measurement System (PPMS, Quantum Design) was used to obtain data at higher temperatures for some samples. The dc magnetic susceptibility χ was measured at 0.1 T in the zero-field-cooled field-heated mode in a vibrating sample magnetometer (VSM, Oxford Instruments). A sample-dependent residual background contribution $\chi_0 \approx 2.09 \cdot 10^{-4}\,\mu_B/\mathrm{f.u.\,T}$ ($x = 0$) and $2.09 \cdot 10^{-4}\,\mu_B/\mathrm{f.u.\,T}$ ($x = 0.144$) independent of temperature was subtracted from the data.

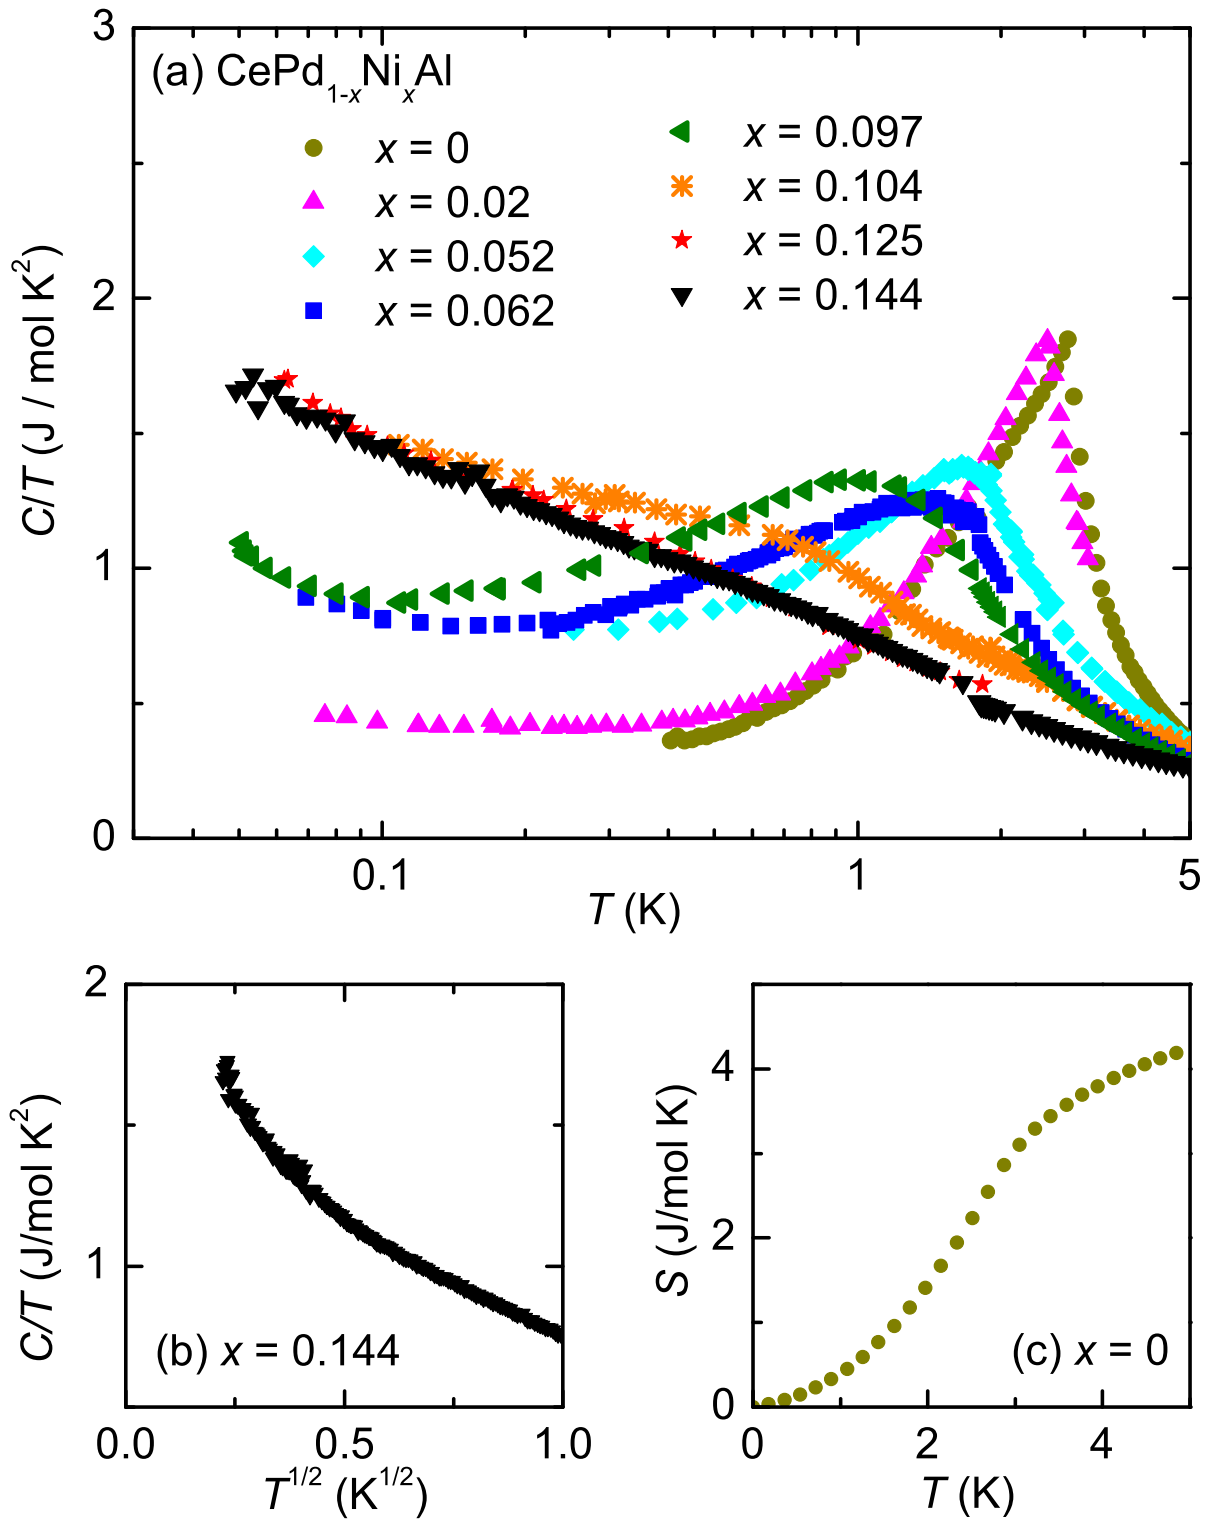

FIG. 2. (a) Specific heat C of CePd$_{1-x}$Ni$_x$Al plotted as C/T versus T. (b) Specific heat C of CePd$_{0.856}$Ni$_{0.144}$Al plotted as C/T versus $T^{\frac{1}{2}}$. (c) Magnetic entropy S versus T for $x = 0$.

The specific-heat data are shown as C/T vs. $\log T$ in Fig. 2. The pure CePdAl compound ($x = 0$) exhibits a sharp anomaly at the Néel temperature $T_{\mathrm{N}} = 2.7$ K in agreement with literature data [32]. The anomaly broadens and moves to lower temperatures with increasing Ni content indicating a suppression of the antiferromagnetic (AF) transition. For the concentration $x = 0.144$, the C/T vs. $\log T$ data follow a straight line in Fig. 2 over almost two decades in temperature in the range $0.05 \leq T \leq 3$ K, i.e., $C/T = a\log(T_0/T)$, with $a = 0.705$ J/mol K^2 and $T_0 = 11.7$ K. The non-Fermi-liquid behavior in the form of a logarithmic divergence of C/T versus T was previously observed in a number of systems, including $\mathrm{CeCu}_{6-x}\mathrm{Au}_x$ for $x = 0.1$ at the concentration-tuned QCP and samples with $x > 0.1$ at the pressure induced QCP [3]. The HMM model [9–11] predicts for 2D antiferromagnets a logarithmic divergence of C/T towards low T near the QCP. Hence the C/T dependence of $\mathrm{CePd}_{1-x}\mathrm{Ni}_x\mathrm{Al}$ can in this model be explained by 2D critical fluctuations, while the HMM prediction for 3D antiferromagnets, $C/T \propto \gamma - a\sqrt{T}$ for $T \to 0$, ist not compatible with our data, as shown in Fig 2 (b). The magnetic entropy S is expected to be $S = R\ln 2 = 5.76\,\mathrm{J/mol\,K}$ for the twofold degenerate crystal-field groundstate of hexagonal CePdAl. Taking into account that one third of the Ce ions remain disordered down to lowest temperatures, one would expect an entropy $S = \frac{2}{3}R\ln 2 = 3.84\,\mathrm{J/mol\,K}$ to be recovered at $T \approx T_\mathrm{N}$. Fig. 2 (c) shows that this is approximately the case for pure CePdAl.

We use the specific-heat data $C(T)$ plotted on a linear scale (not shown) defining T_N as the temperature where $C(T)$ is a maximum for low x. For larger Ni concentrations, however, the small specific-heat anomaly associated with magnetic order resides on a large T-dependent background C_bg, similar to the behavior of $\mathrm{CeCu}_{6-x}\mathrm{Au}_x$ close to the QCP [33]. Hence we assume that the specific heat of the allegedly quantum-critical sample with $x = 0.144$ presents the 'background' that is subtracted from the data of the samples close to x_c and take T_N as the temperature of the maximum of the resulting $\Delta C(T)$ curve. Of course, we can not pin down the critical concentration with absolute accuracy. If the critical concentration would be slightly above 0.144, we estimate for $x = 0.144$ a maximum possible broad anomaly at T_N to $\approx 0.15\,\mathrm{K}$ for this sample. The resulting $T_N(x)$ is shown in Fig. 3 (upper horizontal scale). Up to $x = 0.1$, $T_\mathrm{N}(x)$ nicely follows a straight line as expected for the 2D AF QCP in the HMM model. The deviations towards the QCP possibly signaling a restauration of three-dimensionality, will be discussed below.

In order to compare the x dependence of T_N with the pressure dependence of T_N of pure CePdAl, we determine the effect of unit-cell-volume changes by external hydrostatic pressure p and by chemical pressure. We estimate the compressibility $\kappa = -(1/V)(dV/dp)$ of CePdAl from the bulk moduli B_V of the pure constituents (Voigt-Reuss-Hill approximation) as described in Ref. [34], yielding $B_V = 70.8$ GPa for CePdAl. Direct measurements of the compressibility of CePdAl performed at room temperature yield $B_V = 47.8$ GPa [35]. This value is rather low for HF systems. Furthermore the same authors also report on the pressure dependence of T_N where T_N is found to remain constant up to 0.3 GPa and then decreases at a smaller rate than found in Ref. [22]. We therefore prefer to employ the Voigt-Reuss-Hill approximation. We calculate the unit-cell volume $V(p)$ for each pressure by Goto et al. [22] to obtain $T_\mathrm{N}(V)$ (open symbols in Fig. 3). The unit-cell volume $V(x)$ of $\mathrm{CePd}_{1-x}\mathrm{Ni}_x\mathrm{Al}$ was calculated from our x-ray diffraction data. The resulting $T_\mathrm{N}(V)$ obtained from the data sets $T_\mathrm{N}(x)$ and $T_\mathrm{N}(p)$ can be inferred from the lower horizontal scale of Fig. 3. We find that substituting Pd by Ni yields the same $T_\mathrm{N}(V)$ dependence as applying hydrostatic pressure within the uncertainty of the measurements. This observation suggests that the decrease of T_N with Ni alloying or under pressure is a purely geometric, i.e., volume-dependent, effect. Thus, neither is disorder a driving factor for the suppression of magnetic order, nor can the decrease of T_N be attributed to a large quantitative change of the frustration in this system, since in these cases we would expect strongly different dependencies for $T_\mathrm{N}(p)$ and $T_\mathrm{N}(x)$.

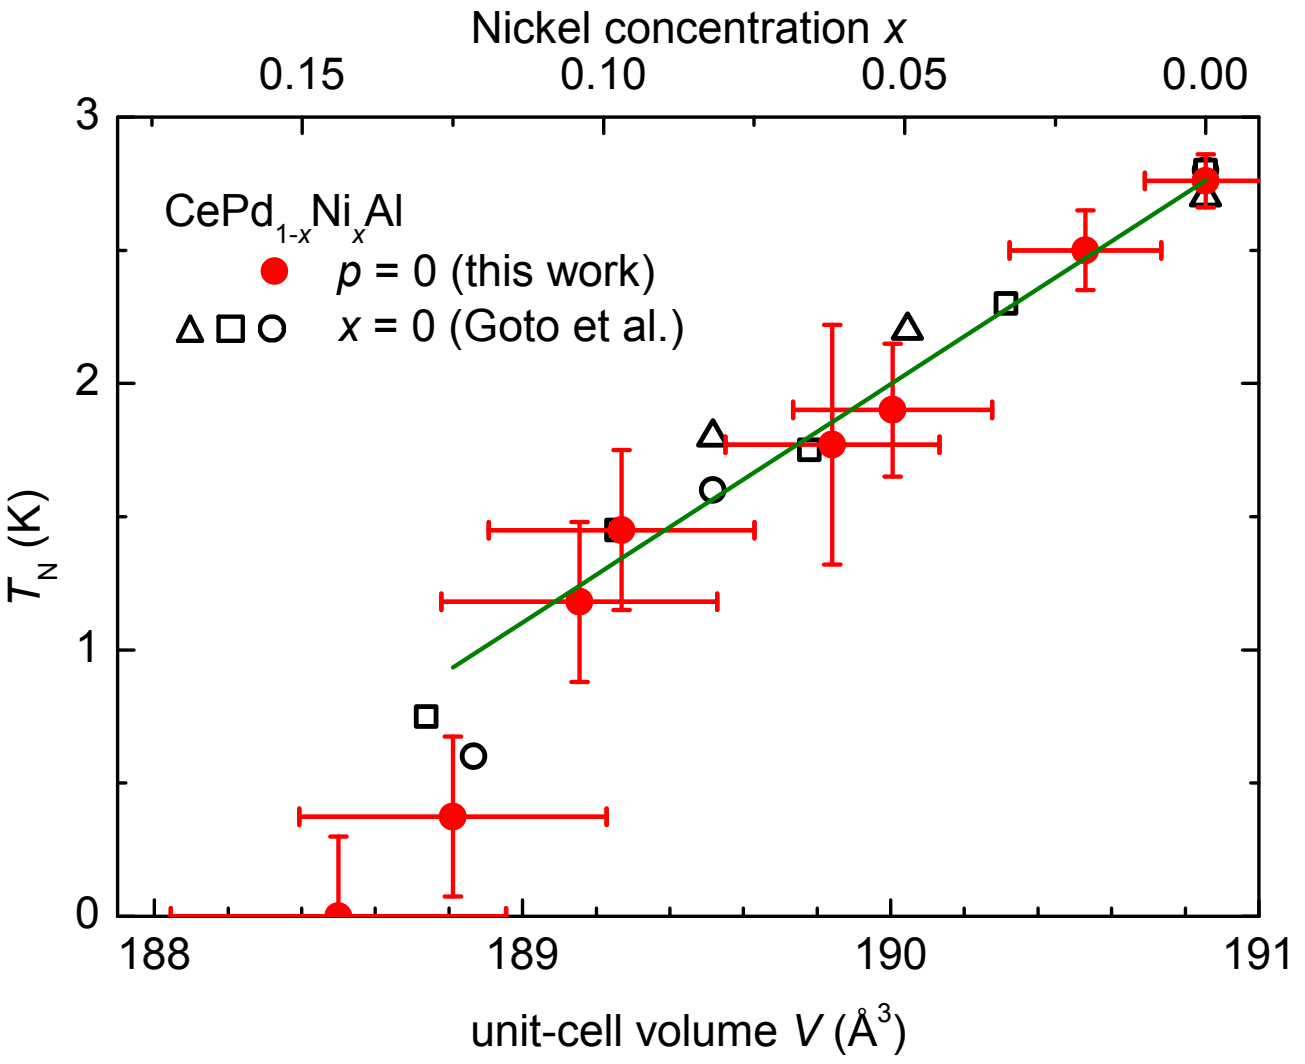

FIG. 3. Néel temperature T_N vs. unit-cell volume V of $\mathrm{CePd_{1-x}Ni_xAl}$ deduced from our data. The data for CePdAl under hydrostatic pressure were taken from Goto et al. [22], (△: magnetic susceptibility, □: electrical resistivity, ○: specific heat), see text for details.

For the discussion of the possible effect of frustration on the QCP of CePdAl, the main problem is how to quantify the degree of frustration. Above we have already dismissed the $T_\mathrm{N}(V)$ dependence on the grounds that this dependence on the unit-cell volume is independent of whether V is changed by hydrostatic pressure or substitution of Pd by Ni. In geometrically frustrated insulating magnetic systems with stable moments, frustration arises from (near) cancelation of competing exchange interactions at the site of a given moment. In this case the frustration parameter ist defined as $f = |\Theta_\mathrm{CW}|/T_\mathrm{N}$, where Θ_CW is the Curie-Weiss temperature derived from the susceptibility in the paramagnetic regime. Using this definition, it could be shown for the poorly metallic $RX\mathrm{Cu}_4$ system with R = rare-earth element and X = In or Cd that there is an approximate inverse relation between f and the electrical conductivity σ, i.e., higher σ leads to lower f (Ref. [36]). If one were to take the same definition of f at face value for $\mathrm{CePd}_{1-x}\mathrm{Ni}_x\mathrm{Al}$, we would have to infer a strong increase of f with x because T_N decreases and $|\Theta_\mathrm{CW}|$ remains roughly constant in the x range investigated here, as is pictured in Fig. 4. Thus, the increase of the ratio $|\Theta_\mathrm{CW}|/T_\mathrm{N}$ with x can not be taken as indicator of increased geometric frustration, it rather reflects the competition between Kondo effect and RKKY interactions. A similar apparent increase of $|\Theta_\mathrm{CW}|/T_\mathrm{N}$ can be infered in $\mathrm{CeCu}_{6-x}\mathrm{Au}_x$, which is a system without geometric frustration.

Fig. 4 serves to illustrate an additional important finding. In the paramagnetic state the effective moment inferred from the slope of $1/\chi$ versus T for $30 < T < 300$ K is practically the same for $x = 0$ and $x = 0.144$. The same holds for the intermediate concentrations [37]. The inset of Fig. 4 reveals that, at low T, a marked difference in the T dependence develops. While $\chi^{-1}(T)$ varies superlinearly for $x = 0$ above T_N, the data for $x = 0.144$ tend to show an exponent smaller than 1. This might possibly point to an anomalous scaling exponent $\alpha \approx 0.9$ as observed for $\mathrm{CeCu}_{6-x}\mathrm{Au}_x$ [5, 6] although neutron scattering experiments are necessary to check this conjecture.

What - then - might be the role of frustration concerning the QCP in CePdAl? We first discuss this issue in terms of the HMM model. While the magnetic structure of CePdAl is three-dimensional in nature with the ordering wave vector $\mathbf{Q} = (\frac{1}{2}\ 0\ \tau)$, our measurements of the specific heat $C/T \propto \ln(T_0/T)$ for $x \approx x_c$ and the linear $T_\mathrm{N}(x)$ dependence are indeed in accord with 2D AF quantum fluctuations in the HMM scenario.

While inelastic neutron scattering experiments are necessary to identify possible 2D planes, our data can already exclude certain possibilities. For a single kagomé-like plane, the magnetic structure can be described by ferromagnetic chains, as mentioned above, that couple only weakly antiferromagnetically by the nnn interaction J_2, because of the frustration of the nn interactions J_1 at the Ce(2) sites [26, 27]. Taking into account the interlayer exchange J_3, the magnetic order can be viewed as a stacking of ferromagnetic chains staggered along the c-direction interrupted by the frustrated Ce(2) moments thus leading to 2D ferromagnetic planes roughly perpendicular to the magnetic ordering wave vector $\mathbf{Q}$. However, 2D ferromagnetic fluctuations will give rise to a specific heat $C/T \propto T^{-\frac{1}{3}}$, which is incompatible with our data. A triple-$\mathbf{Q}$ structure is compatible with the neutron-scattering data if $\tau = \frac{1}{3}$. In this structure, however, AF planes cannot easily identified. In addition the magnetic component τ along the c direction is, in fact, incommensurate and varies slightly with T ($\tau = 0.3535 - 0.3585$ between 0.35 and 2.7 K) [23]. While an incommensuration with small difference of τ from $\frac{1}{3}$ might in principle arise from stacking faults, the temperature dependence of τ is not easy to explain within a triple-$\mathbf{Q}$ structure. Hence within the HMM model, 2D fluctuations confined to AF planes *perpendicular* to the ab plane and separated by frustrated Ce(2) moments, are a viable explanation for the $C/T \propto \log{(T_0/T)}$ behavior.

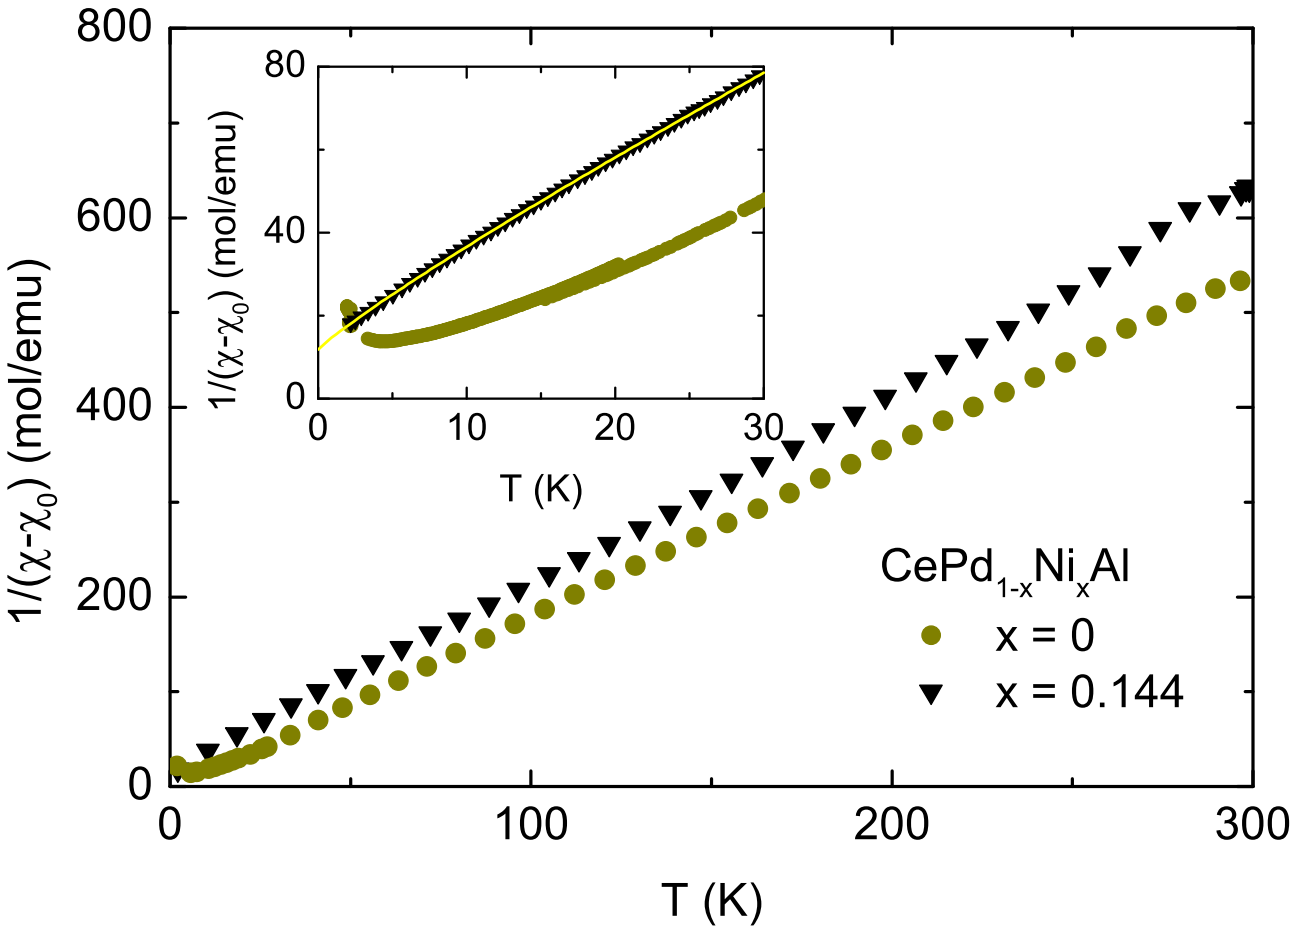

FIG. 4. Inverse susceptibility $(\chi - \chi_0)^{-1}$ of CePdAl and $\mathrm{CePd}_{0.856}\mathrm{Ni}_{0.144}\mathrm{Al}$ versus temperature T. The inset shows the low temperature region below 30 K, where a distinct difference in curvature emerges when approaching the QCP. A sample-dependent residual background contribution (see text) was subtracted from the data. The yellow line shows a fit with an power law $1/\chi + \theta \propto T^{0.9}$.

While in the classical case of an anisotropic 3D system geometric frustration might give way to strictly 2D order, in a quantum system zero-point fluctuations might restore the original dimensionality [38]. This, however, is not always the case. For example, it was shown in the context of a Bose-Einstein condensation of magnetic triplets in $\mathrm{BaCuSi}_2\mathrm{O}_6$ [39] that geometrical frustration yields a reduction of the spatial dimensionality [38, 40]. The partial magnetic frustration in CePdAl appears to reduce the dimensionality by forming frustrated planes from one third of the Ce moments, decoupling the antiferromagnetic planes of the other Ce moments. Thus CePdAl might be a unique system where frustration provides a rationale how a system might find its way from 3D magnetic ordering to 2D criticality. Thus CePdAl might also be a very promising candidate to test the recent predictions for the 2D-3D crossover in terms of the critical quasiparticle theory [41]. The deviations of $T_\mathrm{N}(x)$ from a linear x dependence close to x_c are compatible with such a crossover.

Of course geometric frustration might give rise to additional fluctuations that are not included in the HMM model. Hence other scenarios might be conceivable to explain the quantum critical behavior of CePdAl. Indeed the susceptibility exponent $\alpha < 1$ for $x = 0.144$ could possibly be due to anomalous scaling. Detailed experiments on scaling relations between the energy, temperature and field dependencies as done, e.g., for $\mathrm{CeCu}_{6-x}\mathrm{Au}_x$ [6], are necessary to narrow down the origin of the unusual quantum critical behavior of CePdAl. As a further interesting point, CePdAl offers the possibility of investigating the Kondo effect of geometrically frustrated metals in detail.

In conclusion, we have investigated systematically the effect of chemical pressure on the specific heat of $\mathrm{CePd}_{1-x}\mathrm{Ni}_x\mathrm{Al}$ alloys for Ni concentrations ranging up to $x = 0.144$, where the magnetic order is completely suppressed, giving rise to a QCP. At the concentration-tuned QCP, the $\log(T_0/T)$ dependence of the specific heat suggests, if interpreted within the HMM scenario of conventional quantum criticality, the evolution of 2D magnetic fluctuations. The geometric frustration in this system leading to one third of the Ce moments not participating in long-range AF order, may thus be instrumental in establishing the unusual character of quantum criticality, despite the fact that the magnetic order itself is 3D. On the other hand, the partial order might lead to novel types of excitations close to the QCP not contained in the HMM model that cause the $\log T$ behavior of C/T. Inelastic neutron scattering experiments are planned to test this conjecture. Further investigations on single-crystalline samples of $\mathrm{CePd}_{1-x}\mathrm{Ni}_x\mathrm{Al}$ at different magnetic fields applied along different crystallographic directions are under way in order to clarify the effect of anisotropy on quantum criticality in this partially frustrated system.

We thank J. Schmalian and O. Stockert for fruitful discussions and S. Drobnik for help with some measurements. This work was supported by the Deutsche Forschungsgemeinschaft through FOR 960. H.v.L. thanks the National Science Foundation for partial support of this work under Grant No. PHYS-1066293, and the Aspen Center for Physics for its hospitality.

[1] S. Sachdev, *Quantum phase transitions* (Wiley Online Library, 2007).

[2] S. Sondhi, S. Girvin, J. Carini, and D. Shahar, Reviews of Modern Physics **69**, 315 (1997).

[3] H. v. Löhneysen, A. Rosch, M. Vojta, and P. Wölfle, Rev. Mod. Phys. **79**, 1015 (2007).

[4] O. Stockert, H. v. Löhneysen, A. Rosch, N. Pyka, and M. Loewenhaupt, Phys. Rev. Lett. **80**, 5627 (1998).

[5] A. Schröder, G. Aeppli, E. Bucher, R. Ramazashvili, and P. Coleman, Phys. Rev. Lett. **80**, 5623 (1998).

[6] A. Schröder, G. Aeppli, R. Coldea, M. Adams, O. Stockert, H. Löhneysen, E. Bucher, R. Ramazashvili, and P. Coleman, Nature **407**, 351 (2000).

[7] P. Coleman, C. Pepin, Q. Si, and R. Ramazashvili, J. Phys.: Cond. Mat. **13**, R723 (2001).

[8] Q. Si, S. Rabello, K. Ingersent, and J. Smith, Nature **413**, 804 (2001).

[9] J. A. Hertz, Phys. Rev. B **14**, 1165 (1976).

[10] A. J. Millis, Phys. Rev. B **48**, 7183 (1993).

[11] T. Moriya and T. Takimoto, J. Phys. Soc. Jpn. **64**, 960 (1995).

[12] M. Garst, L. Fritz, A. Rosch, and M. Vojta, Phys. Rev. B **78**, 235118 (2008).

[13] J. Custers, K. Lorenzer, M. Müller, A. Prokofiev, A. Sidorenko, H. Winkler, A. Strydom, Y. Shimura, T. Sakakibara, R. Yu, et al., Nature Materials **11**, 189 (2012).

[14] P. A. Lee, Science **321**, 1306 (2008).

[15] Q. Si, Physica B **378-80**, 23 (2006).

[16] M. Vojta, Phys. Rev. B **78**, 125109 (2008).

[17] P. Coleman and A. Nevidomskyy, J. Low Temp. Phys. **161**, 182 (2010).

[18] M. Kim and M. Aronson, J. Phys.: Condensed Matter **23**, 164204 (2011).

[19] A. Oyamada, K. Kamioka, K. Hashi, S. Maegawa, T. Goto, and H. Kitzawa, J. Phys. Soc. Jpn. **65**, 128 (1996).

[20] A. Dönni, G. Ehlers, H. Maletta, P. Fischer, H. Kitazawa, and M. Zolliker, J. Phys.: Cond. Mat. **8**, 11213 (1996).

[21] Y. Isikawa, T. Mizushima, N. Fukushima, T. Kuwai, J. Sakurai, and H. Kitzawa, J. Phys. Soc. Jpn. **65** Suppl. B, 117 (1996).

[22] T. Goto, S. Hane, K. Umeo, T. Takabatake, and Y. Isikawa, J. Phys. Chem. Sol. **63**, 1159 (2002).

[23] K. Prokeš, P. Manuel, D. Adroja, H. Kitazawa, T. Goto, and Y. Isikawa, Physica B: Condensed Matter **385**, 359 (2006).

[24] A. Oyamada, S. Maegawa, M. Nishiyama, H. Kitazawa, and Y. Isikawa, Phys. Rev. B **77**, 064432 (2008).

[25] P. Villars and K. Cenzual, *Pearson's Crystal Data - Crystal Structure Database for Inorganic Compounds (on CD-Rom),* Release 2011/12, ASM International, Materials Park, Ohio, USA.

[26] M. Núñez-Regueiro, C. Lacroix, and B. Canals, Physica C: Superconductivity **282**, 1885 (1997).

[27] Y. Motome, K. Nakamikawa, Y. Yamaji, and M. Udagawa, Phys. Rev. Lett. **105**, 036403 (2010).

[28] Y. Isikawa, T. Kuwai, T. Mizushima, T. Abe, G. Nakamura, and J. Sakurai, Physica B **281**, 365 (2000).

[29] N. Bagrets, Ph.D. thesis, Universität Karlsruhe (TH), Physikalisches Institut, Karlsruhe, Germany (2009).

[30] High-purity rare-earth metals acquired from Materials Preparation Center, Ames Laboratory, US DOE Basic Energy Sciences, Ames, IA, USA, <http://www.mpc.ameslab.gov>.

[31] A. Gribanov, A. Tursina, E. Murashova, Y. Seropegin, E. Bauer, H. Kaldarar, R. Lackner, H. Michor, E. Royanian, M. Reissner, et al., J. Phys.: Cond. Mat. **18**, 9593 (2006).

[32] C. Schank, F. Jährling, L. Luo, A. Grauel, C. Wassilew, R. Borth, G. Olesch, C. Bredl, C. Geibel, and F. Steglich, J. All. & Comp. **207**, 329 (1994).

[33] H. v. Löhneysen, J. Phys.: Condens. Matter **8**, 9689 (1996).

[34] G. Grimvall, *Thermophysical properties of materials* (The Royal Institute of Technology, Stockholm, Sweden, 1999).

[35] J. Tang, A. Matsushita, H. Kitazawa, and T. Matsumoto, Physica B: Condensed Matter **217**, 97 (1996).

[36] V. Fritsch, J. D. Thompson, J. L. Sarrao, H.-A. Krug von Nidda, R. M. Eremina, and A. Loidl, Phys. Rev. B **73**,

094413 (2006).

[37] V. Fritsch, C.-L. Huang, N. Bagrets, K. Grube, S. Schumann, and H. v. Löhneysen (2012), submitted to Phys. Stat. Sol. (b).

[38] J. Schmalian and C. Batista, Phys. Rev. B **77**, 094406 (2008).

[39] S. Sebastian, N. Harrison, C. Batista, L. Balicas, M. Jaime, P. Sharma, N. Kawashima, and I. Fisher, Nature **441**, 617 (2006).

[40] C. Batista, J. Schmalian, N. Kawashima, P. Sengupta, S. Sebastian, N. Harrison, M. Jaime, and I. Fisher, Phys. Rev. Lett. **98**, 257201 (2007).

[41] E. Abrahams and P. Wölfle, Proceedings of the National Academy of Sciences **109**, 3238 (2012).